

Durability index performance of high strength concretes made basing on different standard Portland cements

Stephen O. Ekolu^a and Sheena Murugan^b

^a*School of Civil and Environmental Engineering, University of the Witwatersrand, Private Bag 3, WITS 2050. stephen.ekolu@wits.ac.za, Tel. +27117177104/21, Fax.+27117177045*

^b*Lafarge Industries SA (pty) Ltd, Private Bag X26, Gallo Manor 2052.*

ABSTRACT

The consortium of three durability index test methods consisting of oxygen permeability, sorptivity and chloride conductivity were used to evaluate the potential influence of four (4) common SANS 10197 cements on strength and durability of concrete. Twenty four (24) concrete mixtures of water-cement ratios (w/c's) = 0.4, 0.5, 0.65 were cast using the cement types CEM I 42.5 N, CEM II/A-M (V-L) 42.5 N, CEM IV/B 32.5R and CEM II/A-V 52.5 N. The concretes investigated fall in the range of the normal strength, medium strength and high strength concretes. Samples were cast into cubes and panels for extraction of the test discs. Other variables investigated were the effect of using filler sand in the mixtures and the influence of compaction method.

It was found that the marked differences in oxygen permeability and sorptivity results observed at normal and medium strengths tended to disappear at high concrete strengths. Also, the influence of the different cement types on the durability properties diminishes at high strengths with a slight bias towards better performance by low strength cement containing higher proportion of extenders. The cements of low strength and/or that contained no extenders (CEM 32.5 R, CEM I 42.5N) showed greater sensitivity to sorptivity relative to other cement types, with water sorptivity values of the former increasing significantly with increase in w/c of the mixtures. Results also show that while concrete resistance to chlorides generally improves with increase in strength, the level of chloride resistance appears to reach a limit beyond which no further improvement is achieved with high strengths. It appears that incorporation of extenders is necessary for superior chloride resistance even with high strengths.

1.0 Introduction

Increased durability requirements and specifications have been quoted for many infrastructural projects in South Africa recently, especially contracts issued by the South African National Roads Agency. Although there has been a lot of research conducted throughout the world on factors affecting durability and durability test methods, limited research has been done in South Africa using local raw materials and test methods. In the 1990's South Africa started developing their own test methods based on the key principles of test methods available internationally. Three tests methods, one for oxygen permeability, another for water sorptivity and the third test being chloride conductivity, were developed together with procedures for preparation of the test specimens [1,2,3,4,8]. Since specifying for durability basing on performance is increasingly becoming the trend, it was decided to study the effects of different South African cement types on concrete durability performance.

The deterioration of concrete is dependent upon one or more transport processes, whether the attack is due to chemical mechanisms such as sulphate attack, delayed ettringite formation, alkali silica reaction, carbonation etc., or due to physical attack processes such as freeze-thaw damage, thermal cracking etc. The transport mechanisms by which aggressive agents can ingress into concrete in form of fluids, gas or liquid are primarily (a) permeability being movement of the media through the pores and cracks of concrete due to pressure differences, (b) diffusion being transportation under concentration gradients, and (c) suction resulting from capillary forces in dry or partially dry materials. The resistance to these transport mechanisms is related to the pore interconnectivity, pore sizes and the tortuosity of pores and cracks. This leads to the importance of design of the concrete mixtures including the kind of material systems used.

2.0 High strength concretes and high performance concretes

High performance concretes (HPCs) and high strength concrete (HSC) are distinct and different types of special concretes and yet a particular mix can contain both characteristics giving high strength and high performance at the same time. Indeed in the past, there have been general perceptions that HPC should have high strength and high durability as stated by Addis [3], that HPC is “*characterized by its strength and durability*”. Others have considered HPC to be synonymous with long service life. The different definitions by various authors for HPC and HSC underscores the difficulties in de-lineating the differences between these two types of concretes. The various definitions can be found summarized in the literature such as [12, 17].

2.1 High performance concretes

The American Concrete Institute (ACI) defines HPC [14] as “*concrete having desired properties and uniformity that cannot be obtained routinely using only traditional constituents and normal mixing, placing and curing practices.*” In other words, the definition broadly considers HPC as all Portland cement concretes whose properties are superior or beyond the normal range of conventional concretes. The definition by the Strategic Highway Research Program (SHRP) is quite prescriptive, stating HPC as *concrete whose strength is greater than 70 MPa, has greater than 80% durability factor under freeze-thaw, and is made with water-cementitious ratio no greater than 0.35* [16]. But it has been shown that concretes of high strengths may show retrogressive performance in durability parameters. For example, concretes of very high early strength are vulnerable to autogeneous and thermal shrinkage. In an experimental study by Shah and Weiss, 2000 [15], it was shown that while decreasing the water-cementitious ratio led to improvement in strength, stiffness and chloride resistance, there was an increase in shrinkage making them more vulnerable to possible early age thermal cracking. Their study was conducted using concretes of w/c's = 0.3, 0.4 and 0.5 with or without silica fume and shrinkage reducing admixture. They recommended that specification of highly durable concrete should at the minimum include three parameters of strength, permeability and early-age cracking. A definition published by the Federal Highway Agency (FHWA) [9] appears to be more plausible, stating HPC as “*concrete that has been designed to be more durable and, if necessary, stronger than conventional concrete*”. In this definition of HPC, durability is advanced as the primary performance criterion while strength is considered a secondary parameter except where it is the definitive property for required performance.

It is clear that HPC is so regarded, for its superior performance with respect to particular critical characteristics of interest to the application. The typical performance properties may include one or more of the following: *high workability, high early or late strength, low permeability, low or high density, low heat of hydration, high resistance to early age cracking, shrinkage and creep, toughness, durability* under severe exposure conditions. Mehta and Monterio, 2005 [13] cites high volume fly ash (HVFA) concrete containing 50 to 70% FA concrete, as an example of a concrete mixture that can be considered HPC concrete due to high crack resistance and durability characteristics resulting from highly reduced water content. And yet the compressive strength of HVFA concrete may be low to medium.

It is evident from various literature sources that the use of the term “performance” with regard to durability of concrete has become synonymous with the incorporation of extenders in the concrete mixture with or without high strength. This is related to the effectiveness of extenders in mitigating most, if not all the major physical or chemical processes that often cause degradation in concretes.

2.2 High strength concretes

HSC is so called, purely on the basis of its high strength development. The enabling technology for HSC came into being when plasticizers and superplasticizers were developed in Japan and Germany in the 1960's, allowing the making of concretes at low water-cement ratios to be possible, a practice which is impossible with conventional concrete. With the use of plasticizing chemical admixtures both high strength and high workability are achieved at the same time.

The definition of HSC has continuously changed while there exists disparity in specifications of the strength levels considered to be the threshold limit/s for HSC. HSC was defined by ACI 363 [5] as *concrete with a cylinder strength greater 41 MPa*. It has recently been speculated that this strength limit may be raised to 55 MPa while ACI 441 [6] puts the strength threshold for HSC at 70/88 MPa. However, it appears to be generally recognized that concretes of compressive strengths 60 to 120 MPa [7,11] are considered HSC's, typically achieved at a low w/c not exceeding 0.35. The advent of HSC has been driven by the need for high strength and stiffness for the ever growing demand in infrastructure especially in the urban areas being constantly under population growth pressures. Consequently, multi-storey structures have become indispensable features needed in the cities. About 30 to 50 years ago most of the tall skyscrapers were constructed mainly using steel. In the present urban centres, concrete has become the dominant construction material for high – storey structures including some of the tallest buildings in the world today. One example of an important application for high strength is that of precast prestressed concrete. The principles of prestressed concrete (PSC) design show that high quality, high strength materials are needed both for steel and concrete. The earlier attempts to produce PSC concrete in the 19th century with low strength materials failed due to the resulting high prestress losses. When high strength steel and concrete were used by Freyssinet in about the 1930's the modern form of PSC was successfully born due to a much reduced prestress loss. This application undercores the typical improvement in material properties of concrete associated with high strength, more especially the improvements in some durability characteristics, creep and shrinkage [10]. The high stiffness and strengths of HSC allows engineers to design members of reduced sectional sizes, utilize space more efficiently and save on the associated construction costs.

The engineering and material properties of HSC are markedly different from those of conventional concrete, hence its treatment as special concrete. It appears that the medium strength concretes in the range of 40 to 60 MPa is a transitional range as properties of normal concretes at about 40 MPa progressively change to distinctively different characteristics at high strength levels. Mcfarlane, 2007 [11] discusses that this transformation may be considered fully achieved at about 80 MPa. At the high strengths of concrete, the difference between cylinder and cube strengths diminish and/or vanish completely unlike in normal concrete where cylinder strength is typically 80% of cube strength. Structurally, concrete becomes brittle with increase in strength, exhibiting a sudden and explosive failure at high strengths. For normal concrete, the stress-strain behaviour is a parabolic or approximately rectangular profile from which the design stress block is derived. At about 100 /120 MPa, HSC exhibits a nearly triangular stress block instead. Accordingly, the design formulae used for conventional structural concrete may not apply to HSC, in which case using the conventional formulae may overestimate the true structural capacity of an HSC member [11].

3.0 Experimental

Four different cement types were selected for the study namely:

- CEM 1 42.5 N Portland cement with about 5% minor additional constituents and a strength enhancer.
- CEM II/A-M (V-L) 42.5N Portland composite cement which incorporates finely ground, high purity limestone interground with Portland cement clinker, 15% quality siliceous fly ash and a strength enhancer.
- CEM IV/B-V 32.5R which incorporates 40% fly ash that is interground with the clinker together with a strength enhancer.
- CEM II/A-V 52.5N which is formulated from Portland cement clinker and between 6 to 20% siliceous fly ash with a strength enhancer.

The aggregates used consisted of 19 mm dolomite stone and 6.7 mm dolomite crusher sand. The filler sand used was a decomposed sandstone material. Twenty four mixes were prepared in total in the laboratory. Mixtures of three different water/cement ratios of 0.4, 0.5, and 0.65 were prepared for each cement type as given in Table 1. The mixes were designed to yield 20 L of concrete with the exception of mixes prepared using CEM IV/B-V 32.5R and CEM I 42.5N incorporating filler sand and which were poked vibrated to simulate site compaction. The latter mixes were cast in panels instead of cubes and hence there were no 28 day compressive strength results tested for the particular mixes.

Twelve test cubes per mix were made. Concrete cubes were demoulded after 24 hours and immediately stored in curing tanks containing portable water which was maintained at $23^{\circ}\text{C} \pm 2^{\circ}\text{C}$ until at the time of testing. The cubes were then tested for compressive strengths at 28 days. Of the cubes prepared, five test cubes were used to determine compressive strength, five test cubes were used for durability testing, and two test cubes reserved in the curing tank. Three of the five test cubes were used for oxygen permeability index testing and water sorptivity, whilst the remainder two test cubes were used for chloride conductivity testing. Test specimens consisting of circular discs (of 70 ± 2 mm in diameter and 30 ± 2 mm in thickness) were prepared by coring and cutting each concrete cube in accordance with the draft standard method for preparation of test specimens [1]. Five cores were taken from each panel. Three cores were used for OPI and sorptivity testing and the other two cores were used for the chloride conductivity tests [1,2,3,4].

Table 1: Mixtures for the various concretes

	Cements: CEM I 42.5N, CEM II/A-V 52.5N, CEM IV/B-V 32.5R, CEM II/A-M (V-L)			Cements: CEM I 42.5N FS, CEM II/A-V 52.5N FS
	w/c = 0.65	w/c = 0.5	w/c = 0.4	w/c = 0.5
Cement (kg)	6.4	7.6	8.7	7.6
Water (kg)	4.2	3.8	3.5	3.8
19mm dolomite stone (kg)	20.3	20.3	20.3	20.3
Dolomite crusher sand (kg)	16.0	16.0	16.0	13
Filler sand (kg)	0	0	0	3.2
Admixture Chryso 209 (mls)	0	0	40	0

4.0 Results and Discussion

4.1 Compressive strength results

Three 28-day cubes of 100 mm size were tested for compressive strength and the results were averaged for each mix. The average compressive strengths obtained have been plotted in the graph shown in Figure 1 (and also presented in Table 1). It can be seen that the three w/c's of 0.4, 0.5 and 0.65 gave concrete strength grades that can be categorized as:

- High strength concrete : 0.4 w/c concrete, 60 to 90 MPa
- Medium strength concrete : 0.5 w/c concrete, 40 to 60 MPa
- Normal strength concrete : 0.65 w/c concrete, 25 to 40 MPa

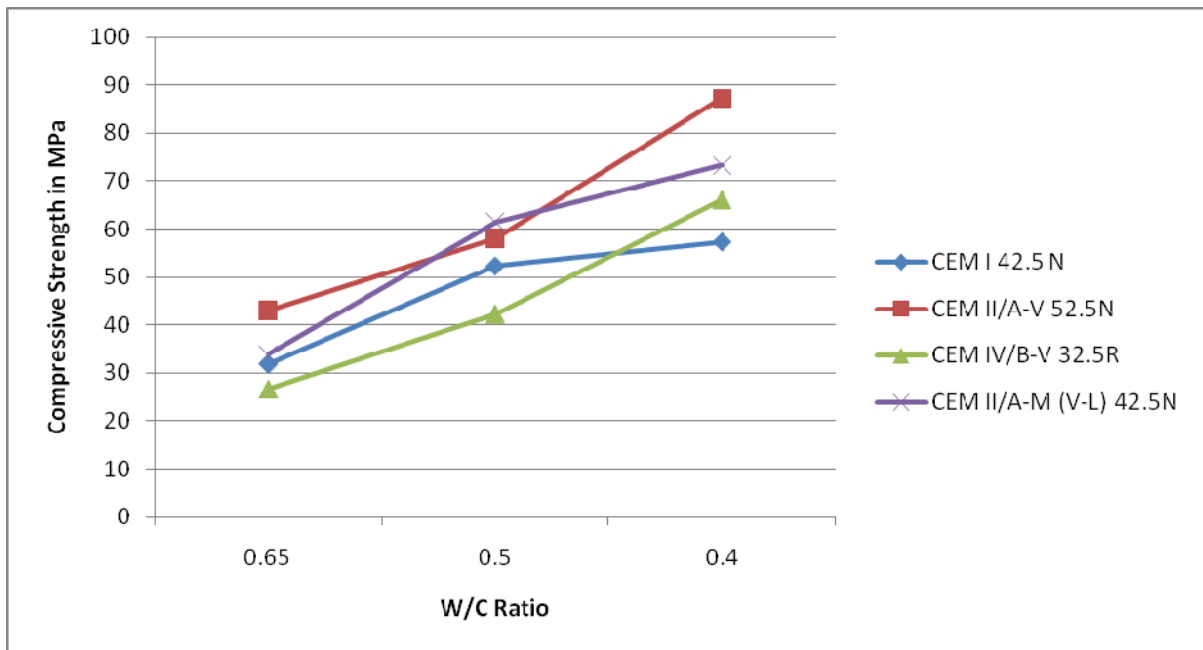


Figure 1: 28- day compressive strengths for different cement types at different w/c ratios

Some mixes were cast at w/c ratio of 0.5, with or without filler sand (FS) to assess the influence of filler sand (see Table 1). The 28-day strength results (see Table 1) seemed to show a trend with higher results for mixes containing a combination of both filler sand and having higher extender contents, that is, for cement types CEM IV 32.5R and CEM II/A-V 52.5N. However, the increases in strengths were small and may be considered negligible. Mixes for cement types CEM I 42.5N and CEM IV/B-V 32.5 R made at w/c ratios of 0.4 were consolidated by vibration and by hand compaction to evaluate possible effects of compaction on durability indices. Interestingly, hand compaction gave slightly higher 28-day strength results compared to vibration (see Table 2).

4.2 Durability test results

As previously mentioned, the consortium of three South African index tests consisting of oxygen permeability, sorptivity, and chloride conductivity were used to assess the durability performance of the concrete mixtures. Table 2 presents the results of all the durability tests conducted on the various concrete mixtures.

4.2.1 Oxygen permeability and water sorptivity

The averaged results for oxygen permeability index (OPI) and water sorptivity (SORP) were plotted in different groupings. Firstly, each cement type was plotted at the three different w/c ratios of 0.65, 0.5 and 0.4 as shown in Figures 2 to 5. This was done in order to observe the trends as influenced by the cement type and w/c ratio. It can be seen that all the OPI results fall within the categories of good ($OPI > 9.5$) and excellent ($OPI > 10$) as per the durability classification in the reference [8]. There seems to be a trend showing that the oxygen permeability index increases as the w/c ratio decreases. However, this trend is not significant due to the closeness of results of the different w/c ratios, although for CEM IV/B-V 32.5R the trend is quite distinct. It is interesting to note that although CEM II A-V 52.5N mix has the highest 28-day strength of up to about 90 MPa, its OPI index is similar or slightly lower than that of CEM IV/B-V 32.5R for the same w/c ratio. In general, the oxygen permeability test results seem to be less sensitive to changes in w/c ratio than changes in cement type.

It is evident that as the water/cement ratio increases, the water sorptivity increases and this trend was quite distinct. It is interesting that the CEM IV/B-V 32.5 R cement type gave the best sorptivity results while all the higher strength cements gave poorer results. At 0.65 w/c ratios, the plain ordinary Portland cement (CEM I 42.5N) mixes gave high water sorptivity values of $SORP = 10.3 \text{ mm/hr}^{0.5}$ which falls under the poor durability class, as compared to the lower values for the cements containing extenders viz:- $SORP = 7.9 \text{ mm/hr}^{0.5}$ for CEM II/A-V 52.5N, $8.7 \text{ mm/hr}^{0.5}$ for CEM II/A-M (V-L) 42.5N, $9.3 \text{ mm/hr}^{0.5}$ for CEM IV/B-V 32.5R. These results suggest that the use of extenders leads to reduction in water sorptivity of the concrete. Also, Figures 2 to 5 show that the water sorptivity test is more sensitive to changes in cement type and water/cement ratios than the oxygen permeability test. The water sorptivity results were also more variable than the oxygen permeability index test results.

Table 2: The 28-day strengths, OPI, water sorptivity and chloride conductivity results for different cement types and different w/c ratios

Cement Type	W/C Ratio	Average 28 day Strengths (MPa)	Average OPI	Average Sorptivity (mm/hr ^{0.5})	Average Chloride Conductivity (mS/cm)
CEM I 42.5N	0.65	31.9	10.0	10.3	2.78
CEM I 42.5N	0.5	52.3	10.2	10.5	2.07
CEM I 42.5N	0.4	57.3	10.4	7.0	1.49
CEM I 42.5N FS	0.5	50.2	10.0	8.2	
CEM I 42.5N FSH	0.5	56.1	10.3	8.5	
CEM I 42.5N H	0.4	68.6	10.7	6.2	
CEM I 42.5N FSP	0.5	55.2	10.2	7.8	
CEM I 42.5N FS Poker Panel	0.5		10.2	8.1	
CEM II/A-V 52.5N	0.65	43.0	10.4	7.9	2.01
CEM II/A-V 52.5N	0.5	58.1	10.5	7.3	1.90
CEM II/A-V 52.5N	0.4	87.2	10.5	7.5	1.60
CEM II/A-V 52.5N FS	0.5	66.2	10.3	9.4	
CEM IV/B-V 32.5R	0.65	26.6		9.3	2.32
CEM IV/B-V 32.5R	0.5	42.3	10.2	6.2	1.57
CEM IV/B-V 32.5R	0.4	66.2	10.6	6.0	1.26
CEM IV/B-V 32.5R FS	0.5	46.8	10.3	7.7	1.73
CEM IV/B-V 32.5R FSH	0.5	50.8			1.82
CEM IV/B-V 32.5R H	0.4	67.6	10.7	6.2	
CEM IV/B-V 32.5R FSP	0.5	49.9	10.3	7.0	1.72
CEM IV/B-V 32.5R FS Poker Panel	0.5		10.6	6.4	
CEM II/A-M (V-L) 42.5N	0.65	33.8	9.6	8.7	2.34
CEM II/A-M (V-L) 42.5N	0.5	61.5	10.0	7.8	1.81
CEM II/A-M (V-L) 42.5N	0.4	73.2	10.2	7.5	1.61
CEM II/A-M (V-L) 42.5N FS	0.5	59.3	10.1	8.2	

FS = filler sand, FSH = filler sand after hand compaction, FSP = filler sand after poor compaction, done simply by lifting the filled concrete mould 20 mm off the floor and dropping it five (5) times.

Figures 6 to 8 gives the trends for the OPI and water sorptivity results for each cement type at a given water/cement ratio. Oxygen permeability results for the blended cement CEM II A-M (V-L) 42.5 N were better than those of CEM I 42.5N. The OPI results for CEM IV/B-V 32.5R mixes of 0.65 w/c were too variable and could not be included in the data. As previously noted, water sorptivity was definitely reduced when using blended cement CEM II A-M (V-L) 42.5 N compared to CEM I 42.5N at w/c = 0.65, which promotes the need to use blended cements in concrete. It can be clearly seen from Figures 6 to 8 that while the performance for the normal and medium strength concretes of 0.65 w/c and 0.5 w/c respectively are sensitive to the cement type used in the mixtures, all the concretes of 0.4 w/c made from the different cement types gave similar OPI values and similar sorptivity indices, indicating that the cement type has little or no significant influence on durability performance of HSC.

4.2.2 Chloride conductivity

Fifteen of the twenty four mixes were tested for chloride conductivity (CLC). The tests included mixes for each cement type covering the three different w/c ratios as shown in Figure 9 (see also Table 2). The different mixes tested include CEM IV B-V 32.5R with concretes of the w/c ratio of 0.5. This cement type generally showed the best durability performance for oxygen permeability and water sorptivity. As expected, the lower w/c ratio of 0.4 gave the lowest and best CLC results for all cement types, the best performing cement being CEM IV/B-V 32.5 R. At w/c ratio of 0.5, CEM IV/B-V 32.5 R had the lowest result but at w/c ratio of 0.65, CEM II/A-V 52.5N had the lowest chloride conductivity result. CEM IV/B-V 32.5R and CEM I 42.5N cements used in the 0.4 w/c concretes gave results falling in the good durability classification [4] while higher w/c's gave poorer chloride indices regardless of the cement type.

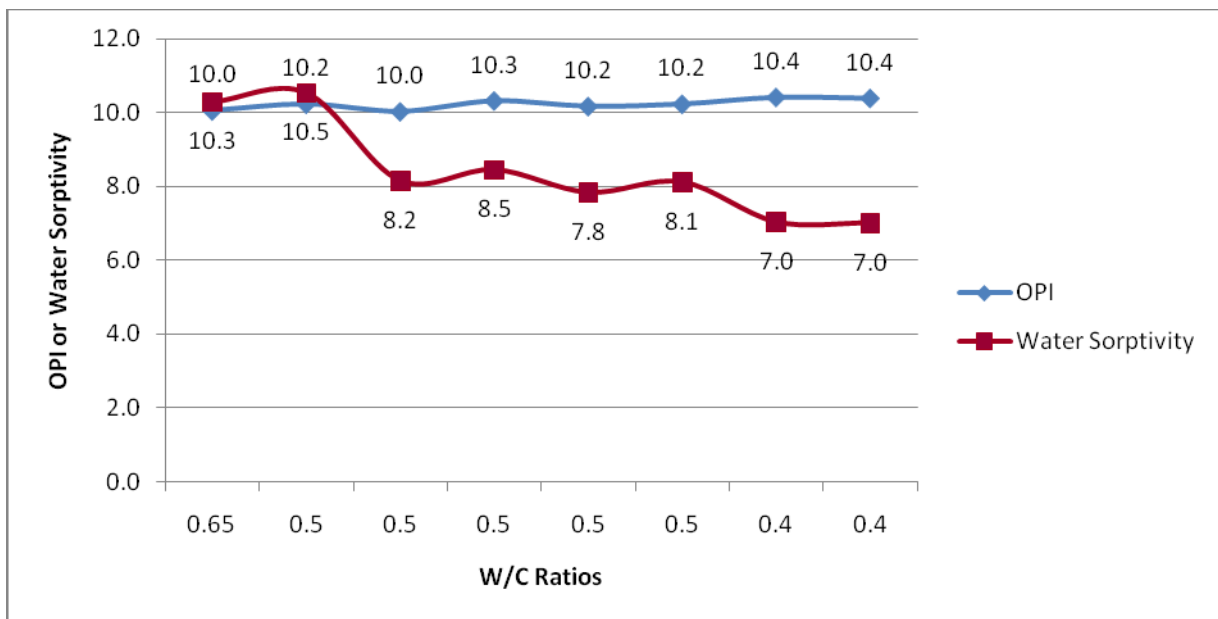


Figure 2: OPI and water sorptivity results for CEM I 42.5N at different w/c ratios

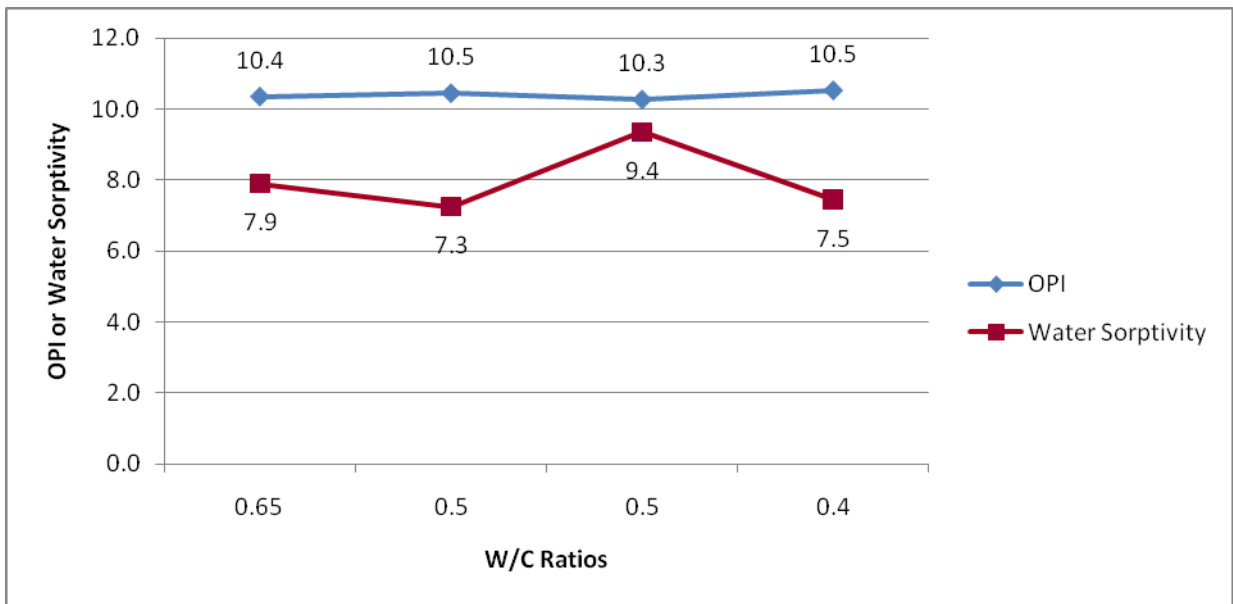


Figure 3: OPI and water sorptivity results for CEM II/A-V 52.5N at different w/c ratios

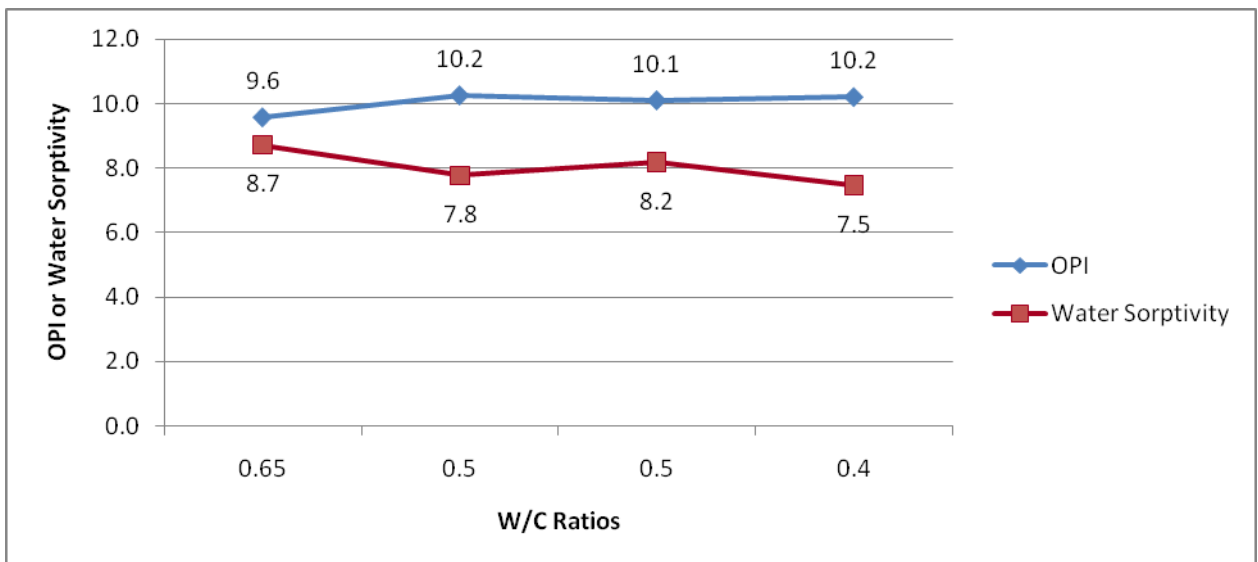


Figure 4: OPI and water sorptivity for CEM II/A-M (V-L) 42.5N at different w/c ratios

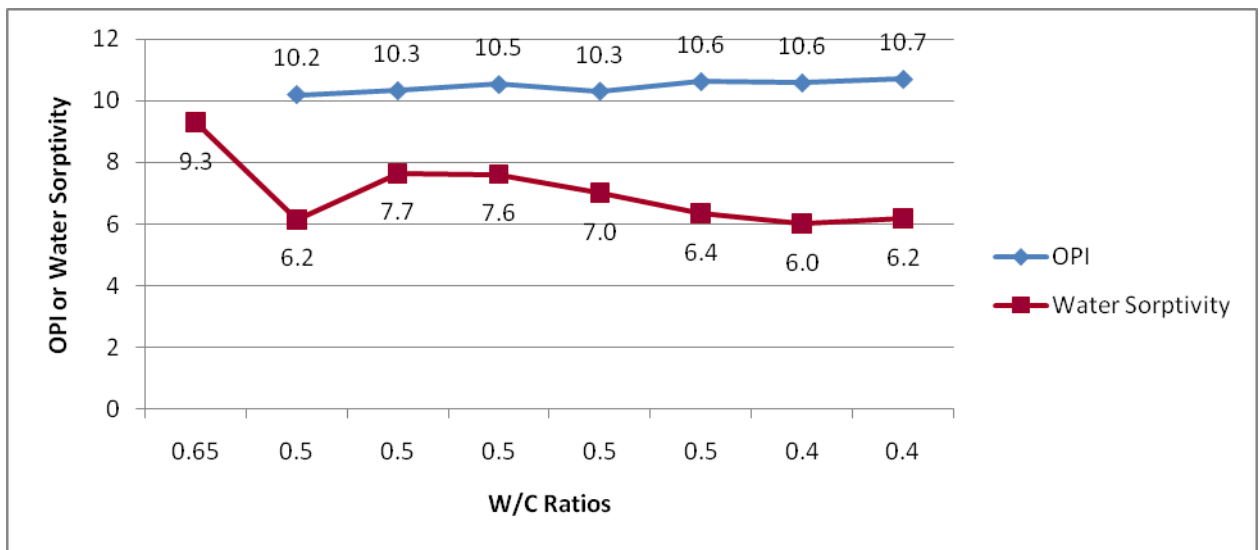


Figure 5: OPI and water sorptivity results for CEM IV/B-V 32.5R at different w/c ratios

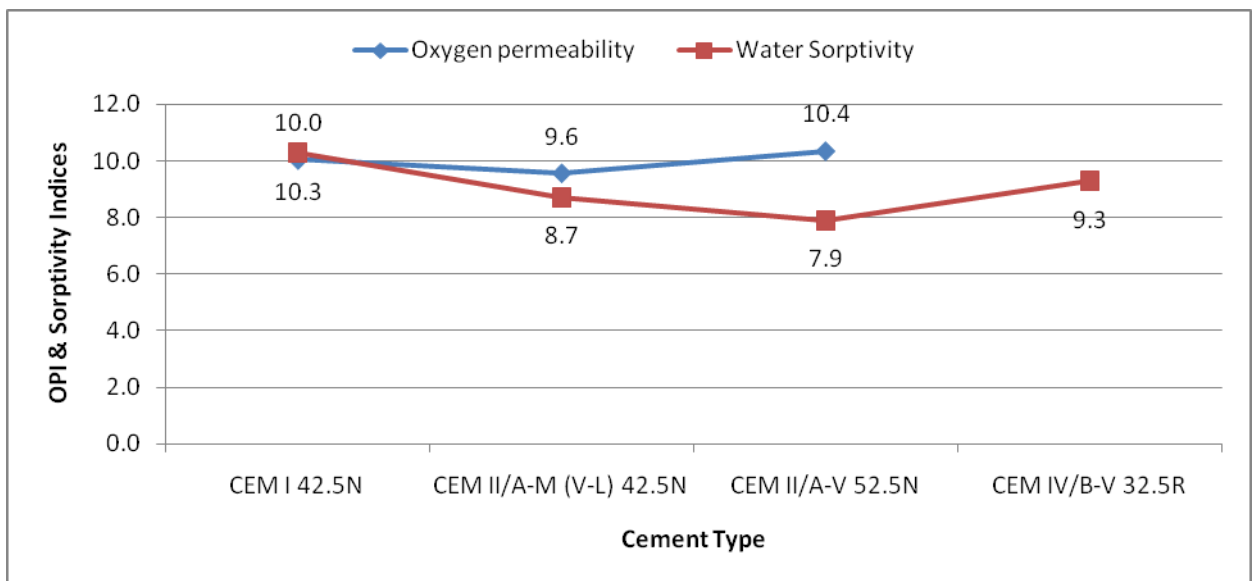


Figure 6: OPI and water sorptivity indices for different cement types at a w/c ratio of 0.65

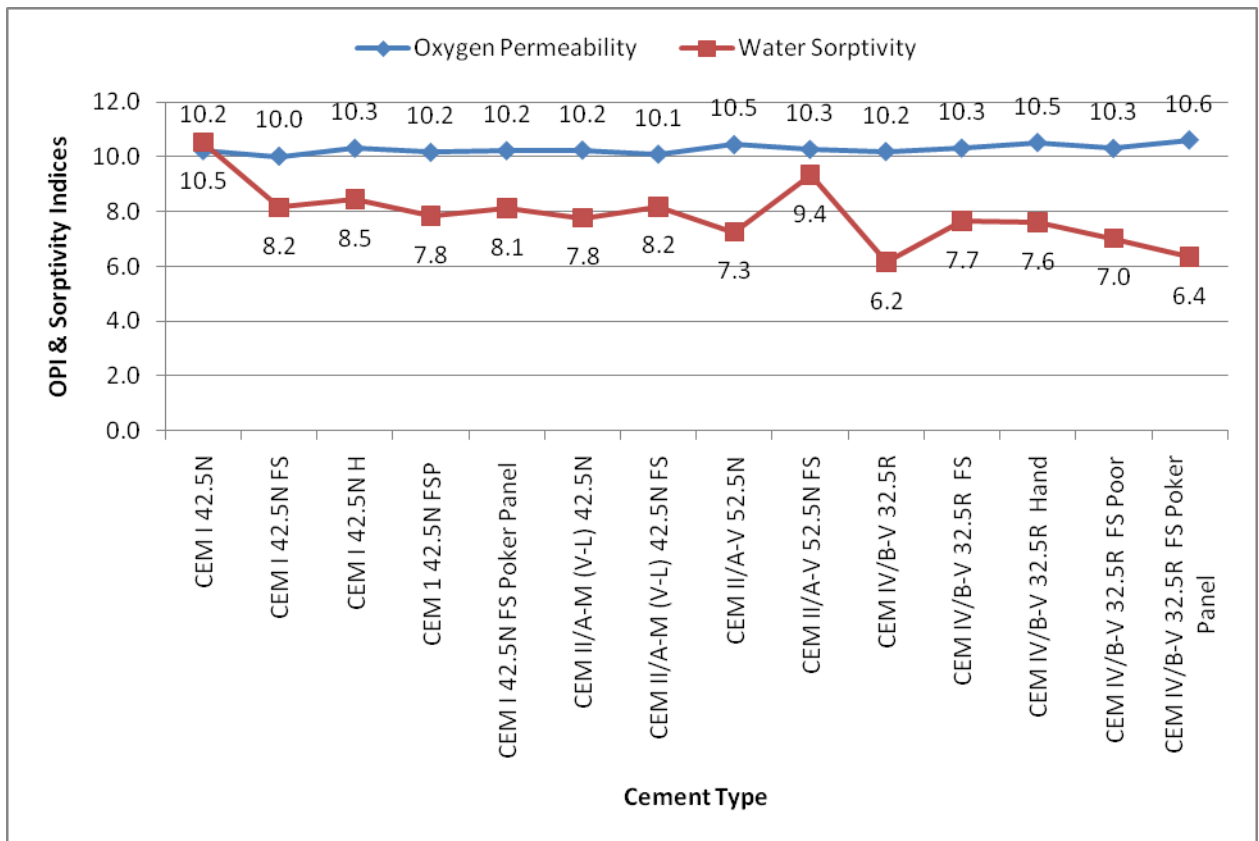


Figure 7: OPI and water sorptivity indices for different cement types at a w/c ratio of 0.5

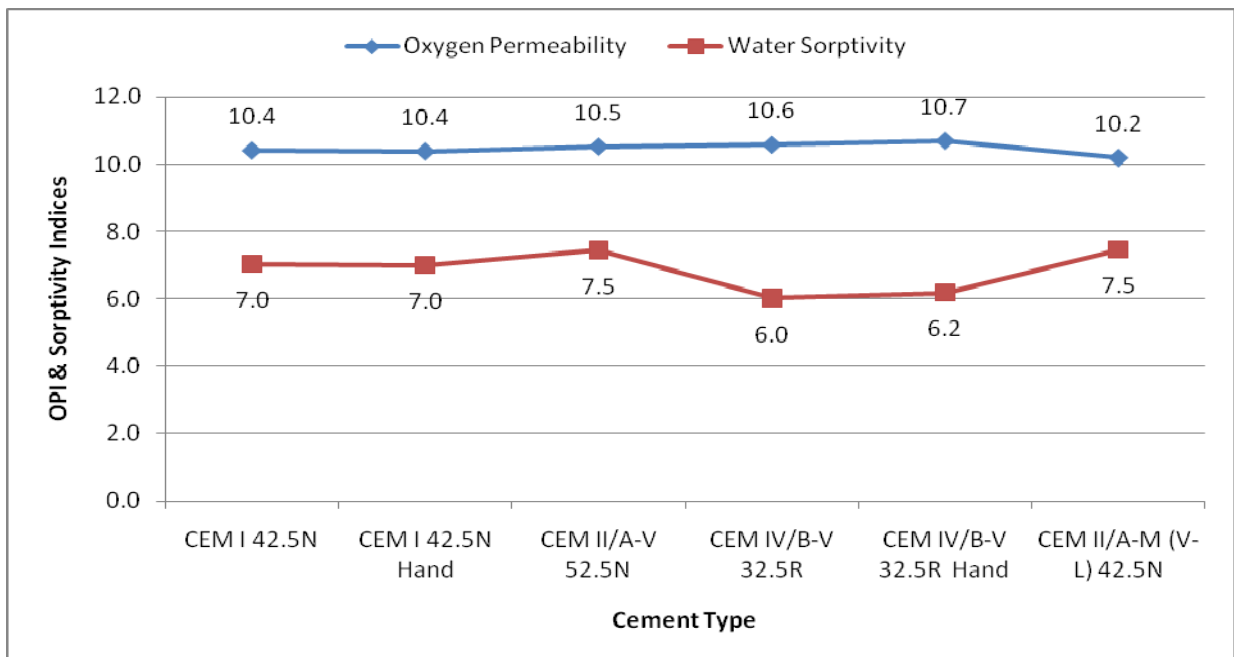


Figure 8: OPI and water sorptivity indices for different cement types at a w/c ratio of 0.4

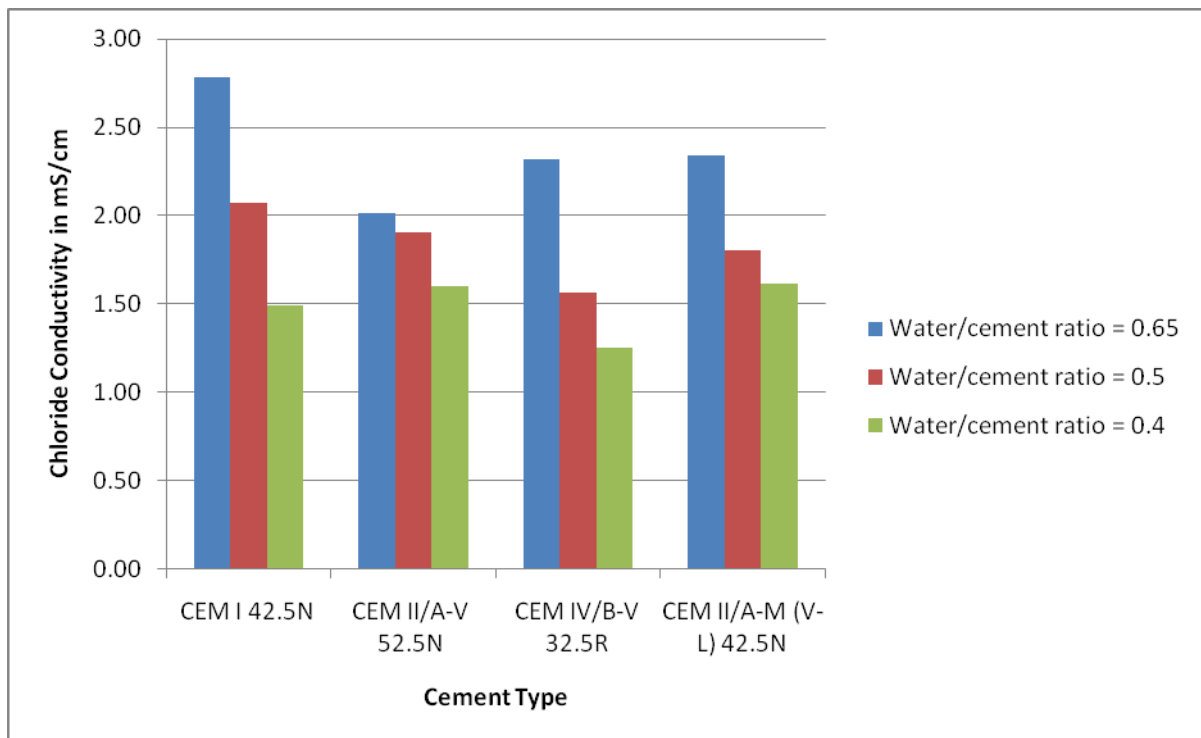


Figure 9: Chloride conductivity results for different cement types and concretes of normal, medium and high strengths

5.0 Conclusions

The following findings have been reached from the foregone investigation:

1. The high strength concretes made from the different cement types gave similar OPI values and similar sorptivity indices with best durability performance being shown by the CEM IV 32.5R. For the normal and medium strengths, plain cement concretes gave higher sorptivity values compared to the cements containing extenders.
2. The results indicate that with high strength concretes, standard cement type has little or no significant influence on permeability and sorptivity. Consistent with these observations, the high strength cement CEM II 52.5 N gave similar OPI results and similar sorptivity indices in all the mixes while the cements of lower strength grades 42.5 N and 32.5 R showed changes (improvement) in index results with decrease in w/c.
3. All the standard cement types used in investigation were found to be capable of producing concretes of high durability performance, the main determining factors being the trade off between the cement type used and mix design associated with w/c of the concrete. These observations may apply to inland environments where carbonation may be considered the predominant cause of corrosion deterioration.

4. The numerical index values of oxygen permeability, found to be in the range of OPI = 10 to 11, and the sorptivity values being 6 to 10 mm/hr^{0.5}, tended to improve with increase in strength up until a seemingly maximum limiting value is reached, beyond which little or no more improvements arise from further strength increase.
5. The CLC indices of the concretes reduced with increase in strength, while the blended cements CEM IV/B-V 32.5R and CEM II/A-V 52.5N gave better overall performance, suggesting that cement types play a significant role and concrete strength has limited control over CLC performance.
6. In all the mixtures, the indices were generally elevated with high strength concrete giving CLC indices in the range of 1.3 to 1.6 mS/cm. These results indicate that the standard cements alone may be inadequate to achieve high CLC performance and will require supplementary blending with higher proportions of extenders in order to achieve superior performance.

6.0 References

- [1] SABS, 'SANS 516-1:2009 Concrete durability index testing', In: Part 1: Preparation of test specimen. (SABS Standards Division; Pretoria, 2009).
- [2] SABS, 'SANS516-2:2009 Concrete durability index test', In: Part 2: Oxygen permeability test. (SABS Standards Division; Pretoria, 2009).
- [3] SABS, 'SANS 516-3:2009 Concrete durability index testing', In: Part 3: Water sorptivity test. (SABS Standards Division; Pretoria, 2009).
- [4] SABS, 'SANS 516-4:2009 Concrete durability index testing', In: Part 4: Chloride conductivity and porosity tests. (SABS Standards Division; Pretoria, 2009).
- [5] ACI 363, State of the Art Report on High Strength Concrete, American Concrete Institute, 1992 re-approved 1997, 55p
- [6] ACI 441: High Strength Concrete Columns: State of the Art Report, Joint ACI-ASCE Committee 441, American Concrete Institute, 1996, 13p
- [7] Addis, Brian J. High performance concrete, unpublished.
- [8] Alexander M.G., Mackechne J.R, Ballim Y., 1999, Guide to the use of durability indexes for achieving durability in concrete structures, Research Monograph No.2, Depts of Civil Engineering, Univ of Cape Town and Univ of the Witwatersrand, 35p.
- [9] Goodspeed, C. H., Vanikar, S., and Cook, R. 1996, High Performance Concrete Defined for Highway Structures, *Concrete International*, Vol. 18, No. 2, February 1996, pp. 62-67.
- [10] Li Jianyong , Yao Yan 2001, A study on creep and drying shrinkage of high performance concrete, *Cement and Concrete Research*, Volume 31, Issue 8, August 2001, Pages 1203-1206
- [11] McFarlane Angus, 2007, High- strength concrete columns: a design guide, *The Structural Engineer*, 20 Mar 2007, p.31-38
- [12] Meeks Kenneth W., Carino Nicholas J., 1999, Curing of high performance concrete: report of the State of the Art, Building and Fire Research Laboratory, National Institute of Science and Technology (NIST), NISTIR 6295

- [13] Mehta P.K, Monterio Paul J.M 2005, Concrete: Microstructure, properties and materials, McGraw-Hill Professional; 3 edition (26 Sep 2005) 659 pages
- [14] Russell, H. G., 1999, ACI Defines High-Performance Concrete, *Concrete International*, Vol. 21, No. 2, February 1999, pp. 56-57.
- [15] Shah, S. P., and Weiss, W. J 2000, High Strength Concrete: Strength, Permeability, and Cracking, Proceedings of the PCI/FHWA International Symposium on High Performance Concrete, Orlando Florida, © 2000, pp. 331-340
- [16] Zia, P., Leming, M. L., and Ahmad, S. H., 1991, "High Performance Concrete -A State-of-the-Art Report," SHRP-C/FR-91-103, North Carolina State University, 246 pp.
- [17] Li Zongjin and Zhang Yunsheng 2005 , High-Performance Concrete: Handbook of Structural Engineering Chapter 15, CRC press, 58p